

**This is an electronic reprint of the original article.
This reprint *may differ* from the original in pagination and typographic detail.**

Author(s): Tatikonda, Rajendhraprasad; Bhowmik, Sandip; Rissanen, Kari; Haukka, Matti; Cametti, M.

Title: Metallogel formation in aqueous DMSO by perfluoroalkyl decorated terpyridine ligands

Year: 2016

Version:

Please cite the original version:

Tatikonda, R., Bhowmik, S., Rissanen, K., Haukka, M., & Cametti, M. (2016). Metallogel formation in aqueous DMSO by perfluoroalkyl decorated terpyridine ligands. *Dalton Transactions*, 45(32), 12756-12762.
<https://doi.org/10.1039/c6dt02008a>


All material supplied via JYX is protected by copyright and other intellectual property rights, and duplication or sale of all or part of any of the repository collections is not permitted, except that material may be duplicated by you for your research use or educational purposes in electronic or print form. You must obtain permission for any other use. Electronic or print copies may not be offered, whether for sale or otherwise to anyone who is not an authorised user.

1

Metallogel formation in aqueous DMSO by perfluoroalkyl decorated terpyridine ligands

Rajendhraprasad Tatikonda, Sandip Bhowmik, Kari Rissanen, Matti Haukka* and Massimo Cametti*

In this paper we introduce a series of stable and thermoreversible metallogels containing terpyridine based ligands with perfluorinated C_8F_{17} tags and $M(II)$ metals.

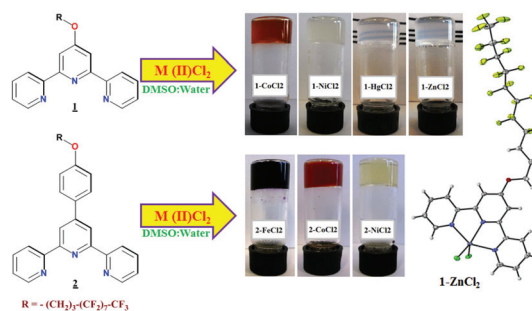

Please check this proof carefully. **Our staff will not read it in detail after you have returned it.**

Translation errors between word-processor files and typesetting systems can occur so the whole proof needs to be read. Please pay particular attention to: tabulated material; equations; numerical data; figures and graphics; and references. If you have not already indicated the corresponding author(s) please mark their name(s) with an asterisk. Please e-mail a list of corrections or the PDF with electronic notes attached – do not change the text within the PDF file or send a revised manuscript. Corrections at this stage should be minor and not involve extensive changes. All corrections must be sent at the same time.

Please bear in mind that minor layout improvements, e.g. in line breaking, table widths and graphic placement, are routinely applied to the final version.

We will publish articles on the web as soon as possible after receiving your corrections; **no late corrections will be made.**

Please return your **final** corrections, where possible within **48 hours** of receipt, by e-mail to: dalton@rsc.org

Queries for the attention of the authors

Journal: **Dalton Transactions**

Paper: **c6dt02008a**

Title: **Metallogel formation in aqueous DMSO by perfluoroalkyl decorated terpyridine ligands**

Editor's queries are marked like this [Q1, Q2, ...], and for your convenience line numbers are indicated like this [5, 10, 15, ...].

Please ensure that all queries are answered when returning your proof corrections so that publication of your article is not delayed.

Query Reference	Query	Remarks
Q1	For your information: You can cite this article before you receive notification of the page numbers by using the following format: (authors), Dalton Trans., (year), DOI: 10.1039/c6dt02008a.	
Q2	Please check that the inserted CCDC numbers are correct.	
Q3	Please carefully check the spelling of all author names. This is important for the correct indexing and future citation of your article. No late corrections can be made.	
Q4	Do you wish to add an e-mail address for the corresponding author? If so, please supply the e-mail address.	

PAPER

Metallogel formation in aqueous DMSO by
perfluoroalkyl decorated terpyridine ligands†

Cite this: DOI: 10.1039/c6dt02008a

Rajendhrasrad Tatikonda,^a Sandip Bhowmik,^a Kari Rissanen,^a Matti Haukka*^a and
Massimo Cametti*^bReceived 19th May 2016,
Accepted 14th July 2016

DOI: 10.1039/c6dt02008a

www.rsc.org/dalton


Terpyridine based ligands **1** and **2**, decorated with a C₈F₁₇ perfluorinated tag, are able to form stable thermoreversible gels in the presence of several d-block metal chloride salts. The gel systems obtained have been characterized by NMR, X-ray diffraction, electron microscopies and *T*_{gel} experiments in order to gain insights into the observed different behaviour of the two similar ligands, also in terms of the effect of additional common anionic species.

Introduction

Over the last few decades, research on gel systems based on low molecular weight gelators (LMWGs) has flourished and has nowadays become an active area of supramolecular chemistry.¹ Soft materials based on gel systems have been progressively used in a wider and wider array of applications ranging from medicine,² catalysis,³ sensing,⁴ and for the formation of hybrid materials.⁵ Especially interesting are metallogel systems,^{1,4b,6,7} where metal ions are incorporated into the soft material, thus providing a way to integrate metal specific properties into gel materials. The advantages of LMWGs over their polymeric counterparts are usually constituted by a fast and enhanced responsiveness towards physical and chemical^{4,7} stimuli and by the possibility to control and modulate gel properties through direct chemical modification at the molecular level. These features derive from the fact that supramolecular gels are formed by small molecules which assemble into fibrillar networks driven by weak non-covalent interactions. In this context, perfluorinated compounds (PFC) have interesting properties, being typically hydrophobic and lipophobic at the same time, and their self-assembly behavior has been extensively studied in order to assess and evaluate the peculiar features of the so called fluororous interactions.⁸ Recently, gelator molecules comprised of perfluorinated moi-

eties have appeared.⁹ Starting from the previous knowledge on metallogel systems based on the terpyridine unit,⁷ we were interested in studying the effect on the gelation properties of combining such a classic moiety¹⁰ with a perfluorinated pendant. Aside from the interest in achieving gels in fluororous solvents,¹¹ fluororous interactions can also be employed for gelation of conventional solvents, often resulting in improved performances over their hydrocarbon counterparts.^{9a}

Herein, we report on a comprehensive study of the gelation capabilities of two novel terpyridine ligands, **1** and **2**, decorated with a C₈F₁₇ perfluorinated tail (Scheme 1) in the presence of divalent d-block metal salts (Fe²⁺, Co²⁺, Ni²⁺, Cu²⁺, Zn²⁺, Cd²⁺ and Hg²⁺) in aqueous DMSO. Depending on the metal used, ligands **1** and **2** can form stable, thermo-reversible gels, featuring extended networks of fibrils tens of micrometers long, visible by SEM and TEM microscopy. Furthermore, we have investigated several aspects which clearly influence the gelation process of **1** and **2** up to its complete inhibition. They are: (i) metal identity, (ii) solvent mixture composition and (iii) counteranion effect. Interestingly, the

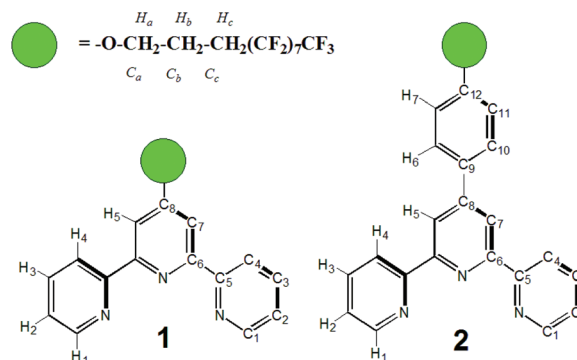Scheme 1 Chemical formulae of ligands **1** and **2**.

^aDepartment of Chemistry, Nanoscience Center, University of Jyväskylä, P.O. Box 35, 40014 Jyväskylä, Finland

^bDepartment of Chemistry, Materials and Chemical Engineering "Giulio Natta" Politecnico di Milano, Via Mancinelli 7, 20131 Milano, Italy

†Electronic supplementary information (ESI) available: Synthesis of **1** and **2**; details of *T*_{gel} experiments, temperature dependent NMR studies; additional SEM and TEM images; crystallographic tables. CCDC 1477308–1477312. For ESI and crystallographic data in CIF or other electronic format see DOI:

10.1039/c6dt02008a

two ligands which differ only for the additional phenyl ring in **2** showed a markedly different behaviour. For example, only ligand **1** is capable of forming gels with Zn^{2+} and Hg^{2+} , while only ligand **2** can form gels with Fe^{2+} , under the experimental conditions tested. This highlights again the need for more comprehensive and systematic studies in order to reach a reliable understanding of the factors which either grant, or inhibit, gelation within LMWG systems.

Results and discussion

Ligands **1** and **2** were synthesized by reacting 1*H*,1*H*,2*H*,2*H*,3*H*,3*H*-perfluoroundecyl iodide with 2,2':6',2''-terpyridin-4'-ol or 4'-(4 hydroxyphenyl)-2,2':6',2''-terpyridine, respectively, under basic conditions in acetone.¹² In a typical gelation experiment, an appropriate amount of solid ligand is placed in a test tube (length 45 mm, *d* 15 mm) and dissolved in DMSO upon heating, whereupon an aqueous solution of the corresponding metal salt is added to reach a final volume of 1 mL. The mixture is then heated to obtain a clear solution which, as it cooled down to room temperature, would remain as such, or lead to a precipitate, or afford a translucent gel. In all cases presented in Table 1, a metal to ligand ratio equal to 1 was employed. The first comment concerns the tested solvents. No gels were obtained by using DMSO only (or other common solvents such as MeOH, MeCN and DMF and their aqueous mixtures), however, in a 9 : 1 DMSO : water mixture, ligand **1** forms a gel in the presence of ZnCl_2 and HgCl_2 , while ligand **2** forms a gel with FeCl_2 (Fig. 1a). Minimum gelation concentrations (mgc) are around 0.3 wt% in all cases (Table 1). Interestingly, we were not able to obtain gels with ligand **1** and FeCl_2 , nor gels with ligand **2** and ZnCl_2 or HgCl_2 . The increase of water content up to 20% and 30% allowed us to obtain gels with CoCl_2 and NiCl_2 with both ligands. Thus, the DMSO : water ratio is a crucial parameter that must be taken into account, in line with other studies previously published.^{6b,13} Considering the effect exerted by water onto the gelation outcome and the fact that at a lower water content both Co^{2+} and Ni^{2+} in the presence of the ligands afforded clear solutions, it seems that water makes the ligand/salt mixture less

Table 1 Gelation studies for ligands **1** and **2** in the presence of 1 equivalent of different metal(II) chloride salts in various DMSO : water solvent mixtures (mcg in parenthesis expresses as wt%) [S = solution; P = precipitate; PG = partial gel; G = gel]

	FeCl_2	CoCl_2	NiCl_2	CuCl_2	ZnCl_2	CdCl_2	HgCl_2
DMSO : water 9 : 1							
1	P	S	S	P	G (0.3%)	P	G (0.3%)
2	G (0.3%)	S	S	P	P	P	P
DMSO : water 8 : 2							
1	P	G (0.4%)	S	P	G (0.2%)	P	G (0.2%)
2	G (0.2%)	G (0.3%)	PG	P	P	P	P
DMSO : water 7 : 3							
1	P	G (0.4%)	G (0.3%)	P	G (0.2%)	P	G (0.2%)
2	G (0.2%)	G (0.3%)	G (0.3%)	P	P	P	P

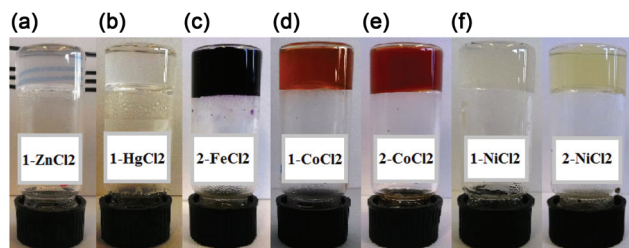


Fig. 1 Photographs of the gel systems: (a) 1- ZnCl_2 , (b) 1- HgCl_2 , and (c) 2- FeCl_2 in a 9 : 1 DMSO : water mixture; (d) 1- CoCl_2 and (e) 2- CoCl_2 in an 8 : 2 DMSO : water mixture and (f) 1- NiCl_2 and 2- NiCl_2 in a 7 : 3 DMSO : water mixture.

solvated and more prone to aggregation. Also, under no tested conditions we were able to obtain gels with CuCl_2 and CdCl_2 .

As all the gels were thermo-reversible, a series of experiments were carried out in order to determine T_{gel} with the inverted test tube method. The tubes were sealed to prevent solvent evaporation. All gels present a T_{gel} temperature which is directly proportional to the gelator content, in particular, increasing it from 0.4 to 0.8 wt% leads to a T_{gel} increase in the range between 5 and 16 °C, the latter increment occurring in the 1- NiCl_2 case (7 : 3 DMSO : water). In general, it seems that a higher water content leads to an improved stability. In order to check this hypothesis, the 1- ZnCl_2 and 2- FeCl_2 gel systems were studied in more detail and the water content was taken as well into consideration for the T_{gel} measurements (Fig. 2). The data clearly show that increasing both the gelator and the water content (up to 30%) leads to a plateau of stability, which however abruptly collapses when 40% water content is reached for the more concentrated samples. A similar behaviour was found for the 2- FeCl_2 gel systems where, however, such a clear plateau of stability is not observed (see Fig. S1, ESI†).

Additional information on these gel systems was also acquired by electron microscopy on xerogel samples, giving

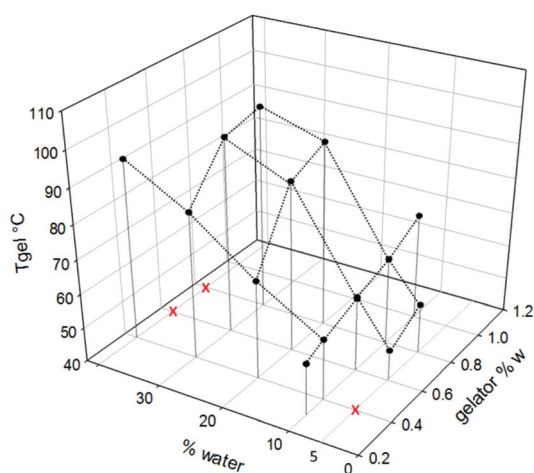


Fig. 2 Graphical representation of the conditions viable to gel formation for the 1- ZnCl_2 system and their corresponding T_{gel} . The red crosses denote precipitation.

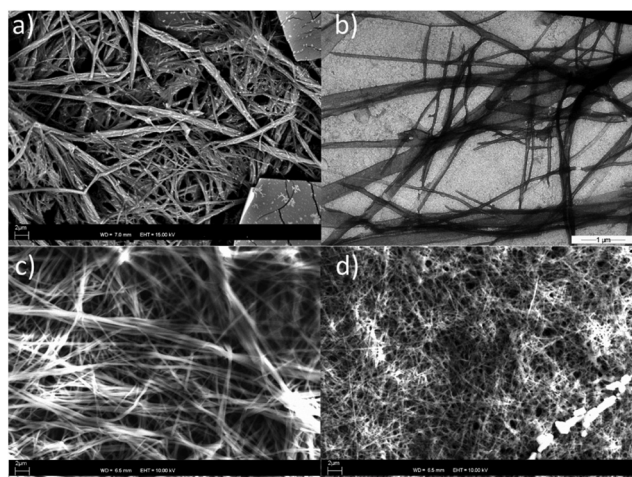


Fig. 3 SEM and TEM images of metallogeles with ligand **1**: (a) SEM image of **1-ZnCl₂** in a 9 : 1 DMSO : water mixture; (b) TEM image of **1-ZnCl₂** in a 9 : 1 DMSO : water mixture; (c) SEM image of **1-CoCl₂** in an 8 : 2 DMSO : water mixture; (d) SEM image of **1-NiCl₂** in a 7 : 3 DMSO : water mixture.

insights on the gel morphology. All samples presented abundant fibrillary networks (Fig. 3 and S3, ESI[†]), however, distinct structural differences were observed depending on the given ligand/metal combination. Thinner fibres and higher aspect ratios were observed for samples made with **2** compared to those with **1**. The typical gel fibers were cylindrical with the diameter varying in the 50–100 nm range, while Zn(II) produced much larger tape-like structures. A last comment is given for the **1-HgCl₂** system, which has a particular behaviour, in that, despite its initial stability, we have observed that it completely loses its gel character to yield a micro-crystalline material in a few hours time. This prevented the preparation of the sample for electron microscopy analysis which showed no fibers, rather several microcrystals by SEM (Fig. 4S, ESI[†]).

As said, the data reported so far are related to samples where a metal to ligand ratio was maintained equal to 1 : 1. In order to ascertain that the actual gelator unit is a 1 : 1 metal complex of **1** and **2**, as strongly suggested by previous work on the gel system derived from terpyridine metal complexes,⁷ we have also tested the **1-ZnCl₂** system using 1 : 2 and 2 : 1 metal to ligand ratios at 0.4 wt% of the ligand (which equals the mgc for a 1 : 1 sample). No gel was observed with the 1 : 2 ratio sample, while gel formed with 2 : 1 ratio. Compounds **1** and **2** are strongly coordinating ligands, and thus these data lead to the straightforward conclusion of a gelating unit made of a 1 : 1 complex. As the sub-stoichiometric metal quantity does not allow for gelation, it means that not enough complex is formed to warrant reaching its mgc. We would like to point out that this behaviour can be so easily rationalized due to the high stability of terpyridine metal complexes, while more careful analyses are needed when dealing with less efficiently coordinating ligands.^{6b}

Gel systems **1-ZnCl₂** and **2-FeCl₂** were also studied by temperature dependent ¹H-NMR. Fig. 4 (panel A) displays the com-

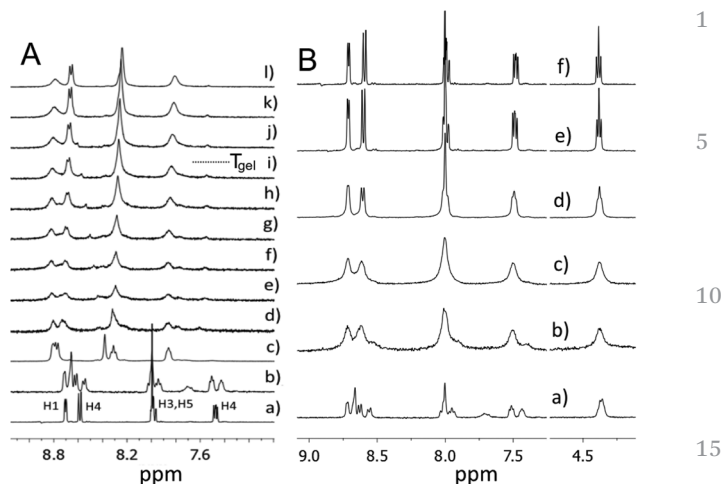


Fig. 4 Panel A: ¹H-NMR spectra of (a) **1** at 80 °C; (b) **1** at 25 °C and (c) after addition of 1 eq. of ZnCl₂; (d–l) temperature dependent spectra of **1-ZnCl₂** gel system (from 35 °C to 75 °C, 5 °C step increase). Panel B: Temperature dependent ¹H-NMR spectra of ligand **1** (conc. = 1.4 × 10⁻² M) in DMSO-d₆ from 25°).

parison between the spectra of ligand **1** in DMSO-d₆ at 80 °C (a) and at 25 °C (b), the spectrum of **1** after the addition of 1 equivalent of ZnCl₂ (under the mgc) at 25 °C (c) and the spectra of the **1-ZnCl₂** gel system at various temperatures from 25 °C to 75 °C (from d to l). First of all, ligand **1** shows significant tendency for aggregation as several additional peaks appear in its spectrum at 25 °C (Fig. 4, panel A, spectrum b) if compared with that at 80 °C (Fig. 4, panel A, spectrum a) (*vide infra*). More so, the addition of Zn²⁺ metal ions shifts all peaks downfield in the aromatic region, as expected due to metal coordination (Fig. 4, panel A, spectrum c). Once the gel is formed (Fig. 4, panel A, spectrum d), evident broadening and an S/N decrease are observed. Such spectral appearance persists also after T_{gel} (57.8 °C in this case) and this indicates a strong aggregation tendency.

Given the ample evidence of the important role of anions in gelation processes,^{1g,4a,6b,14} we tested the effect of the addition of 2 equivalents of other common anions, such as

Table 2 Effect of the addition of different anionic species to various L-MCl₂ gel systems (L = **1**, **2**; M = Zn(II), Hg(II), Fe(II), Co(II), Ni(II))

		Br ⁻	I ⁻	NO ₃ ⁻	AcO ⁻	SCN ⁻	ClO ₃ ⁻
1	Zn	P	G	G	P	P	G
	Hg	P	P	G	G	P	G
	Co	G	G	G	G	G	G
	Ni	G	G	G	G	P	G
2	Fe	G	P	G	G	G	P
	Co	G	P	G	G	P	P
	Ni	P	P	G	G	P	P

In the case of the NiCl₂ gel, the ratio of the solvent mixture is DMSO : water 7 : 3, while in all other cases it is 8 : 2. P = precipitate, G = gel.

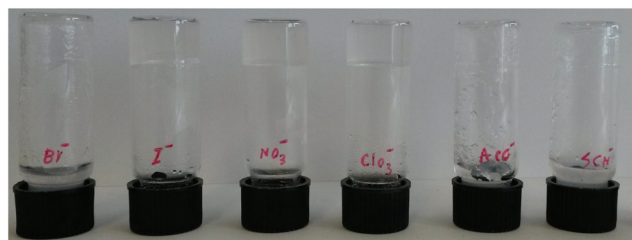


Fig. 5 Photographs of the effect of the addition of 2 equivalents of different anionic species to the 1-ZnCl₂ gel system.

Br⁻, I⁻, NO₃⁻, AcO⁻, SCN⁻ and ClO₃⁻ (added as sodium salts) to 4 wt% 7 : 2 DMSO–water gel samples (see Table 2).

Fig. 5 shows the outcome of such test experiments for the 1-ZnCl₂ system, where the presence of Br⁻, AcO⁻ and SCN⁻ anions clearly leads to a complete loss of gelation attitude, while I⁻, NO₃⁻ and ClO₃⁻ do not visibly alter the system. By comparison with the other gels made with ligand 1, we observed that NO₃⁻ and ClO₃⁻ are the ions which have less influence on the system, while SCN⁻ is the anion which most frequently leads to gel disruption (3 out of 4 of the cases). Most interestingly, in the case of ligand 2, it is the ClO₃⁻ anion which induces gel collapse (Table 2, Fig. S5 and S6†). The striking difference with what observed with ligand 1 could be hardly explained if not by recalling that gelation is generated by a subtle balance between the system solvation and crystallization propensity, and small variations in the ligand structure can be significant.

Data reported in Table 2 also show that 1-CoCl₂ is the most stable system under the tested conditions as it can withstand all kinds of anion interference, among those tested (Fig. S7, ESI†). This is also confirmed by the following experiment, aimed to test the effect of additional Cl⁻ anions on the gel system, where increasing amounts of Cl⁻ anion (as TBA salt) were added to the gel systems (Fig. 6).¹⁵

For the 1-ZnCl₂ gel system, the presence of additional 10 equivalents of Cl⁻ anion prevents the gel formation. Less

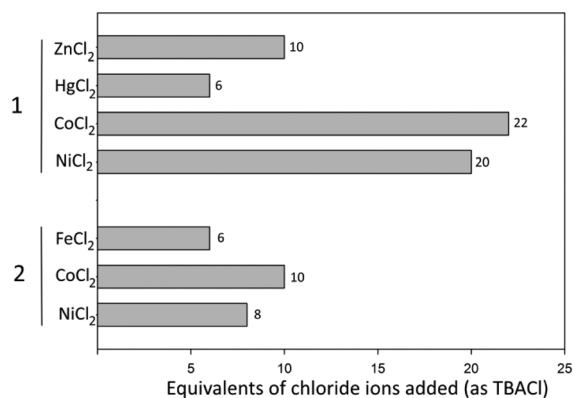


Fig. 6 Limit of gel stability upon addition of TBACl (starting composition of the gel = 0.8 wt%); DMSO : water solvent mixture = 9 : 1 for Zn(II), Fe(II) and Hg(II); 8 : 2 for Co(II) and 7 : 3 for Ni(II).

stable than that are the 1-HgCl₂ and 2-FeCl₂ systems whose gelation is inhibited at 6 equivalents. On the other hand, 1-NiCl₂ and, in particular, 1-CoCl₂ show enhanced stability as their gels can be still obtained in the presence of additional 19 and 21 equivalents of Cl⁻ ions, respectively. Surely, the higher water content in these two gel systems has a role in the observed stability, however, if these data are collectively analysed, they point to an intrinsic higher stability of 1-CoCl₂, if compared to the other gel systems. Also, it can be reasonably stated that ligand 1 forms more stable gels than ligand 2 (see Table 2 and Fig. 6). This could be due to a higher tendency of 1 to aggregate, as mentioned above. Temperature dependent ¹H-NMR spectra of 1 in DMSO-d₆ are reported in Fig. 4 (panel B).

Indeed, the spectrum recorded at 25 °C (Fig. 4, panel B, spectrum a) clearly shows additional peaks which can be attributed to aggregated species. The temperature increase initially leads to peak broadening (Fig. 4, panel B, spectra b and c) and then to the non-aggregated species (Fig. 4, panel B, spectra e and f), featuring well shaped and narrow peaks. Also ligand 2 shows this behaviour, but to a lesser extent (Fig. S9, ESI†). The high aggregation tendency of 1 is also confirmed by concentration dependent experiments (Fig. S10, ESI†) and by DOSY (Fig. 7). The latter technique shows a fast equilibrium between free and aggregated ligand species, with a progressive reduction of the diffusion coefficient upon concentration increase ($-\log D$ from 9.47 to 9.71). An intrinsic higher tendency for aggregation for 1 could be the reason for the generally more stable gels observed with this ligand. The same conclusions could be drawn by concentration dependent

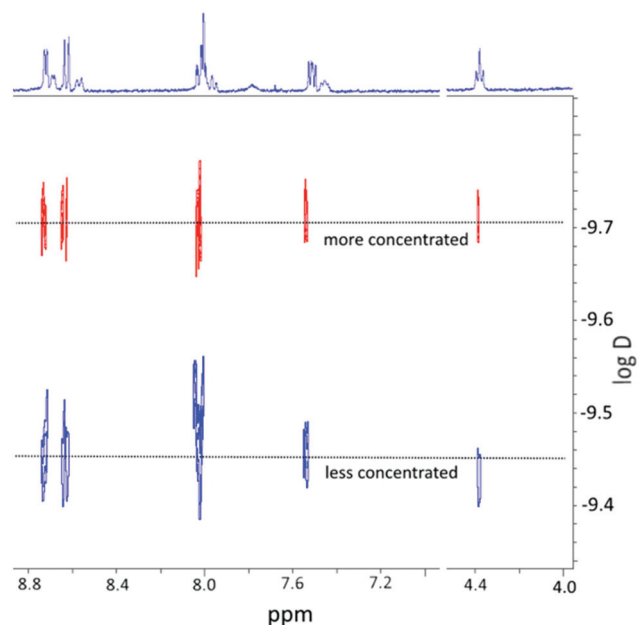


Fig. 7 ¹H-DOSY plot of 1 at 4.7×10^{-3} M and 1.4×10^{-2} M concentration. Top projection shows the more concentrated sample (pulse sequence: ledbppg2s; $T = 302$ K, $n_s = 16$; $TD(f1) = 16$). Processed with TopSpin software.

¹⁹F-NMR experiments, although the observed shifts are small (see Fig. S11 in the ESI†).

We were also able to obtain single crystals of good quality suitable for X-ray diffraction structural determination for complexes **1**-ZnCl₂ (and **1**-ZnBr₂), **1**-HgCl₂ and also for **1**-CuCl₂.¹⁶ As a reminder, the **1**-ZnCl₂ and **1**-HgCl₂ systems form a gel, the addition to **1**-ZnCl₂ of 2 equivalents of Br⁻ leads to a precipitate, while no gel is formed with CuCl₂, so that if any structural elements were responsible for the behaviour observed, the analysis of the X-ray determined structures of the above complexes should be revealing. In fact, as shown in Fig. 8, the solid state characterization of both gelating (**1**-ZnCl₂ and **1**-HgCl₂) and non-gelating systems (**1**-ZnBr₂ and **1**-CuCl₂) gives very similar results in terms of molecular complex and packing organization as well. All four complexes, regardless of the metal identity, display pentacoordination which can be viewed as a distorted trigonal bipyramidal type.¹⁷ This is exerted by the classical NNN chelation from the terpyridine moiety and by two additional halide ions which complete a N₃X₂ coordination sphere. As far as the packing of the fluorinated chains is concerned, type I C-F...F-C inter-chain geometries are mainly observed within the lattice, with C-F...F angles in the ca. 120–155° range.¹⁸

Finally, the X-ray powder diffraction pattern of the **1**-ZnCl₂ xerogel sample was compared with the simulated pattern obtained from the single crystal X-ray structure of the ZnCl₂ complex with ligand **1**. Indeed, this test could be very telling about the presence of similar packing patterns between the gel and the solid states.¹⁹ As probably expected, considering the

strong similarity among the solid state structures found for gelating and non-gelating systems, a modest match is found (see Fig. S13 in the ESI†), also due to the presence of some amount of amorphous phase. As observed in other cases,¹⁹ this could be also due to the formation of other phases during the preparation of the xerogel sample.

Conclusions

In conclusion, we have developed novel ligands **1** and **2**, that feature a terpyridine moiety decorated with a perfluorinated C₈F₁₇ tag, and tested their gelating properties in the presence of a series of d-block metal ions. Thermo-reversible LMWG metallo-gel systems were obtained in aqueous DMSO (up to 30% v/v of water) in the case of ligand **1** with Co(II), Ni(II), Zn(II) and Hg(II), and ligand **2** with Fe(II), Co(II) and Ni(II), depending on the DMSO:water ratio employed. These gel systems were studied with a combination of electron microscopies, X-ray diffraction, *T*_{gel} experiments and NMR spectroscopy, where not only the metal identity but also the counteranion effect and the solvent composition were taken into account. Despite the similar structure of the two ligands, **1** was not able to form gels with Fe(II) ions, while **2** was not able to form gels with either Zn(II) or Hg(II), indicating an intrinsic different selectivity pattern for the two ligands. Also, based on *T*_{gel} experiments and its tolerance to a larger amount and variety of anionic species, ligand **1** can be considered as being forming more stable gel systems. This can also be related to a more pronounced tendency to aggregate.

Given the absence of major structural characteristics that could explain the different responses of **1** and **2** to metal ions in terms of gelation, the systems reported here illustrate again how subtle structural differences could lead to significantly different outcomes.

Experimental methods

Synthesis

All chemicals were purchased from chemical sources and used without purification. DMSO for the gelation test was ACS reagent grade (≥99.9%). The ligands **1** and **2** were synthesized by adopting a modified literature procedure.²⁰ 4'-(4-Hydroxyphenyl)-2,2':6',2''-terpyridine was synthesized by adopting a literature procedure.²¹ Assignment for ¹H- and ¹³C-NMR signals was carried out by 2D COSY and HMQC techniques (see the ESI†).

1: a mixture of 2,6-bis(2-pyridyl)-4(1*H*)-pyridone (125 mg, 0.5 mmol), K₂CO₃ (207 mg, 1.5 mmol), and a catalytic amount of 18-crown-6 in 30 mL of acetone was stirred at room temperature for 1 h. After that, ¹H,¹H,²H,²H,³H,³H-perfluoroundecyl iodide (295 mg, 0.502 mmol) in 2 mL of acetone was added dropwise to the above reaction mixture at room temperature. Then, the reaction mixture was refluxed for 2 days. 20 mL of water was added to the above reaction mixture, and extracted

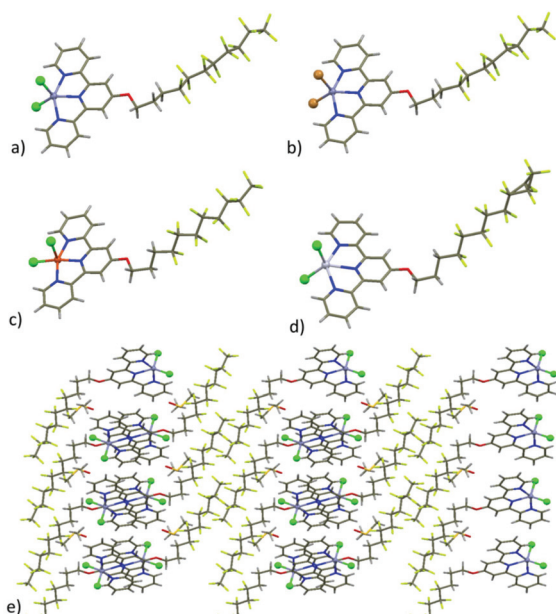


Fig. 8 X-ray structures of (a) **1**-ZnCl₂ complex, (b) **1**-ZnBr₂ complex, (c) **1**-CuCl₂ complex, (d) **1**-HgCl₂ complex and (e) packing of **1**-ZnCl₂ complex. Colour code: H = light grey; C = dark grey; O = red; N = blue; Cl = green; F = yellow; Zn = grey-blue; I = purple; Cu = dark orange; Br = light brown.

with CH₂Cl₂ (3 × 20 mL) and dried under vacuum. Yield: 342 mg (96.5%); ¹H NMR (400 MHz, CDCl₃) δ 8.68 (ddd, *J*_{ortho} = 4.8 Hz, *J*_{meta} = 1.8 Hz, *J*_{para} = 1.0 Hz, **H**₁, 2H), 8.64 (dt, *J*_{ortho} 8.0 Hz, *J*_{meta} = 1.0 Hz, *J*_{para} = 1.0 Hz, **H**₄, 2H), 8.02 (s, **H**₅, 2H), 7.87 (td, *J*_{ortho} = 8.0, *J*_{ortho} = 8.0 Hz, *J*_{meta} = 1.8 Hz, **H**₃, 2H), 7.35 (ddd, *J*_{ortho} = 8.0 Hz, *J*_{ortho} = 4.8 Hz, *J*_{meta} = 1.8 Hz, **H**₂, 2H), 4.32 (t, *J* = 4.9 Hz, **H**_a, 2H), 2.43–2.30 (m, **H**_c, 2H), 2.22–2.15 (m, **H**_b, 2H); ¹³C NMR (101 MHz, CDCl₃) δ 166.76 (**C**₈), 157.16, 155.88, 149.02 (**C**₁), 136.83 (**C**₃), 123.91 (**C**₂), 121.34 (**C**₄), 107.20 (**C**₇), 66.49 (**C**_a), 29.70, 27.90 (t, *J* = 23 Hz), 20.45 (t = 3.8 Hz); ¹⁹F NMR (282 MHz, CDCl₃) δ –81.13, –114.61, –121.99, –122.21, –123.02, –123.72, –126.41. ESI-TOF-MS Calcd for [M + H]⁺ (C₂₆H₁₇F₁₇N₃O)⁺: 710.1100; found: 710.1080.

2: the synthetic procedure was similar to that of **1**, except that the starting material 4'-(4 hydroxyphenyl)-2,2':6',2''-terpyridine was used instead of 2,2':6',2''-terpyridin-4'-ol. Yield: 385 mg (~98%); ¹H NMR (400 MHz, CDCl₃) δ 8.76 (ddd, *J*_{ortho} = 4.8, *J*_{meta} = 1.8, *J*_{para} = 1.1 Hz, **H**₁, 2H), 8.73 (s, **H**₅, 2H), 8.70 (dt, *J*_{ortho} = 8.0, *J*_{meta} = 1.1 Hz, *J*_{para} = 1.1, **H**₄, 1H), 7.90 (m, **H**₃ and **H**₇, 4H), 7.38 (ddd, *J*_{ortho} = 8.0, *J*_{ortho} = 4.8 Hz, *J*_{meta} = 1.1 Hz, **H**₂, 2H), 7.08–7.01 (d, *J* = 9 Hz, **H**₆, 2H), 4.14 (t, *J* = 5.9 Hz, **H**_a, 2H), 2.43–2.30 (m, **H**_c, 2H), 2.20–2.12 (m, **H**_b, 2H); ¹³C NMR (100 MHz, CDCl₃) δ 159.47 (**C**₁₂), 156.35, 155.86, 149.66, 149.10 (**C**₁), 136.87 (**C**₃), 131.16, 128.60 (**C**₁₁), 123.78 (**C**₂), 121.38 (**C**₄), 118.29 (**C**₇), 114.79 (**C**₁₀), 66.42 (**C**_a), 29.70, 28.01 (t, *J* = 23 Hz), 20.61. ESI-TOF-MS Calcd for [M + H]⁺ (C₃₂H₂₁F₁₇N₃O)⁺: 786.1413; found: 786.1402.

X-ray structure determination

The crystals of ligand **2**, 1-ZnCl₂, 1-HgCl₂, 1-ZnBr₂ and 1-CuCl₂ were immersed in cryo-oil, mounted in a MiTeGen loop and measured at 120–123 K. The X-ray diffraction data were collected on an Agilent Technologies Supernova diffractometer using MoKα or CuKα radiation. The CrysAlisPro²² program packages were used for cell refinements and data reductions. Structures were solved by a charge flipping method using the SUPERFLIP²³ program or by direct methods using the SHELXS-2008²⁴ program. An analytical, Gaussian, or multi-scan (CrysAlisPro²²) absorption correction was applied to all data. Structural refinements were carried out using SHELXL-2014²⁴ or SHELXL-2015²⁴ software. In structure 1-HgCl₂, fluorine atoms F5–F13 and F15–F17 as well as the carbon atom C25 were disordered over two sites with equal occupancies. Distances C21–F5, C21–F5B, C21–F6, C21–F6B, F5–F6 and F5B–F6B were restrained to be similar. In all cases hydrogen atoms were refined using the riding model. The crystallographic details of ligand **2**, 1-ZnCl₂, 1-HgCl₂, 1-ZnBr₂ and 1-CuCl₂ are summarized in Table 1 in the ESI.†

The NMR spectra (¹H, ¹³C and ¹⁹F) of ligands were recorded on a Bruker Avance DRX 400 NMR spectrometer and chemical shifts were expressed in ppm (δ C₆H₅F internal standard = –113.6 ppm). The mass spectrum was recorded on Micromass (ESI-TOF-MS). SEM and TEM images were recorded on a Bruker Quantax400 EDS (Zeiss EVO-50XVP) and a JEOL JEM-1400HC respectively. X-Ray powder diffraction analysis was performed with a PANalytical X'pertPRO diffractometer.

Acknowledgements

Mr Petri Papponen and Mr Hannu Pakkanen are kindly acknowledged for their help with SEM and TEM measurements. M. C. thanks the Programma per Giovani Ricercatori “Rita Levi Montalcini” – 2009; M. H. and R. T. would like to acknowledge EU COST Action 1302 “Smart Inorganic Polymers”.

Notes and references

- (a) L. A. Estroff and A. D. Hamilton, *Chem. Rev.*, 2004, **104**, 1201–1218; (b) M.-O. M. Piepenbrock, G. O. Lloyd, N. Clarke and J. W. Steed, *Chem. Rev.*, 2010, **110**, 1960–2004; (c) S. S. Babu, V. K. Praveen and A. Ajayaghosh, *Chem. Rev.*, 2014, **114**, 1973; (d) R. G. Weiss, *J. Am. Chem. Soc.*, 2014, **136**, 7519; (e) C. Tomasini and N. Castellucci, *Chem. Soc. Rev.*, 2013, **42**, 156; (f) L. E. Buerkle and S. J. Rowan, *Chem. Soc. Rev.*, 2012, **41**, 6089; (g) R. G. Weiss and P. Terech, *Molecular Gels: Materials with Self-Assembled Fibrillar Networks*, Springer, Dordrecht, The Netherlands, 2006; (h) *Functional Metallosupramolecular Materials*, ed. J. G. Hardy and F. H. Schacher, RSC, Cambridge UK, 2015.
- (a) K. Y. Lee and D. J. Mooney, *Chem. Rev.*, 2001, **101**, 1869–1879; (b) E. Busseron, Y. Ruff, E. Moulin and N. Giuseppone, *Nanoscale*, 2013, **5**, 7098–7140.
- (a) J. F. Miravet and B. Escuder, *Chem. Commun.*, 2005, 5796–5798; (b) J. Potier, S. Menuel, M.-H. Chambrier, L. Burylo, J.-F. Blach, P. Woisel, E. Monflier and F. Hapiot, *Catal.*, 2013, **3**, 1618–1621.
- (a) Z. Džolić, M. Cametti, A. D. Cort, L. Mandolini and M. Zinic, *Chem. Commun.*, 2007, 3535–3537; (b) B. Xiao, Q. Zhang, C. Huang and Y. Li, *RSC Adv.*, 2015, **5**, 2857–2860.
- M. Cametti and Z. Džolić, *Chem. Commun.*, 2014, **50**, 8273–8286.
- (a) J. Zhang and C.-Y. Su, *Coord. Chem. Rev.*, 2013, **257**, 1373–1408; (b) M. Cametti, M. Cetina and Z. Džolić, *Dalton Trans.*, 2015, **44**, 7223–7229; (c) Z. Džolić, M. Cametti, D. Milic and M. Zinic, *Chem. – Eur. J.*, 2013, **19**, 5411–5416.
- (a) S. Bhowmik, B. Nath Ghosh and K. Rissanen, *Org. Biomol. Chem.*, 2014, **12**, 8836; (b) B. Nath Ghosh, S. Bhowmik, P. Mal and K. Rissanen, *Chem. Commun.*, 2014, **50**, 734.
- (a) A. Varadwaj, P. R. Varadwaj and B.-Y. Jina, *RSC Adv.*, 2016, **6**, 19098–19110; (b) H. Omorodion, B. Twamley, J. A. Platts and R. J. Baker, *Cryst. Growth Des.*, 2015, **15**, 2835–2841; (c) C. Adam, L. Yang and S. L. Cockcroft, *Angew. Chem., Int. Ed.*, 2015, **54**, 1164–1167; (d) R. J. Baker, P. E. Colavita, D. M. Murphy, J. A. Platts and J. D. Wallis, *J. Phys. Chem. A*, 2012, **116**, 1435–1444; (e) M. Cametti, B. Crousse, P. Metrangolo, R. Milani and G. Resnati, *Chem. Soc. Rev.*, 2012, **41**, 31–42.
- (a) H. Kumari, S. E. Armitage, S. R. Kline, K. K. Damodaran, S. R. Kennedy, J. L. Atwood and

- 1 J. W. Steed, *Soft Matter*, 2015, **11**, 8471; (b) A. N. Khan, M. Schmutz, J. Lacava, A. A. Ouahabi, T.-T.-T. Nguyen, P. J. Mesini and J.-M. Guenet, *Langmuir*, 2015, **31**, 7666–7672; (c) S. Banerjee, V. M. Vidya, A. J. Savyasachi and U. Mitra, *J. Mater. Chem.*, 2011, **21**, 14693–24705; (d) C. Ren, S. Xu, J. Xu, H. Chen and H. Zeng, *Org. Lett.*, 2011, **13**, 3840–3843.
- 5
- 10 Terpyridines belong to one of the most widely utilized class of ligands for the formation of transition metal complexes, often employed as building blocks in supramolecular chemistry; see for example: H. Hofmeier and U. S. Schubert, *Chem. Soc. Rev.*, 2004, **33**, 373–399.
- 15
- 11 (a) J. Loiseau, M. Lescanne, A. Colin, F. Fages, J. B. Verlhac and J. M. Vincent, *Tetrahedron*, 2002, **58**, 4049–4052; (b) M. George, S. L. Snyder, P. Terech and R. G. Weiss, *Langmuir*, 2005, **21**, 9970–9977; (c) J. Gan, M. El Bakkari, C. Belin, C. Margottin, P. Godard, J.-L. Pozzo and J.-M. Vincent, *Chem. Commun.*, 2009, 5133–5134.
- 20
- 12 Y.-R. Hong and C. B. Gorman, *J. Org. Chem.*, 2003, **68**, 9019–9025.
- 25
- 13 (a) C. Liu, Q. Jin, K. Lv, L. Zhang and M. Liu, *Chem. Commun.*, 2014, **50**, 3702; (b) N. Yan, Z. Xu, K. K. Diehn, S. R. Raghavan, Y. Fang and R. G. Weiss, *J. Am. Chem. Soc.*, 2013, **135**, 8989; (c) J. Lu, J. Hu, C. Liu, H. Gao and Y. Ju, *Soft Matter*, 2012, **8**, 9576; (d) A. Pal and J. Dey, *Langmuir*, 2011, **27**, 3401.
- 30
- 14 (a) G. O. Lloyd and J. W. Steed, *Nat. Chem.*, 2009, **1**, 437–442; (b) M.-O. M. Piepenbrock, N. Clarke and J. W. Steed, *Langmuir*, 2009, **25**, 8451–8456.
- 35
- 15 In this experiment, the possible dilution effect has been taken care of by employing a more concentrated gel system (0.8 wt%) so that the ligand concentration is always above the mcg, even after the addition of increasing aliquots of (TBA)Cl. Metal : ligand ratio is 1 : 1 in all cases.
- 5
- 16 Single crystals of 1-ZnX₂ (X = Cl or Br) and 1-CuCl₂ were obtained from DMSO, 1-HgCl₂ was grown from acetonitrile, and ligand 2 was crystallized from chloroform. Additional details are given in the ESI.†
- 10
- 17 1-CuCl₂ could also be viewed as square pyramidal.
- 15
- 18 (a) P. Panini and D. Chopra, in *Hydrogen Bonded Supramolecular Structures*, ed. Z. Li and L. Wu, Springer-Verlag, Berlin, Heidelberg, 2015, lecture notes in chemistry 87; (b) R. J. Baker, P. E. Colavita, D. M. Murphy, J. A. Platts and J. D. Wallis, *J. Phys. Chem. A*, 2012, **116**, 1435–1444.
- 20
- 19 (a) U. Kumar Das, D. R. Trivedi, N. N. Adarsh and P. Dastidar, *J. Org. Chem.*, 2009, **74**, 7111–7121; (b) P. Sahoo, N. N. Adarsh, G. E. Chacko, S. R. Raghavan, V. G. Puranik and P. Dastidar, *Langmuir*, 2009, **25**, 8742–8750; (c) A. Ballabh, D. R. Trivedi and P. Dastidar, *Chem. Mater.*, 2006, **18**, 3795–3800.
- 25
- 20 Y.-R. Hong and C. B. Gorman, *J. Org. Chem.*, 2003, **68**, 9019–9025.
- 30
- 21 J. Wang and G. S. Hanan, *Synlett*, 2005, 1251–1254.
- 35
- 22 Agilent, *CrysAlisPro*, Agilent Technologies Inc., Yarnton, Oxfordshire, England, 2013.
- 40
- 23 L. Palatinus and G. Chapuis, *J. Appl. Crystallogr.*, 2007, **40**, 786.
- 45
- 24 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2008, **64**, 112.
- 50
- 55